

Organic Superconductors: Reduced Dimensionality and Correlation Effects

C. Bourbonnais

Centre de Recherche en Physique du Solide, Université de Sherbrooke, Sherbrooke, Québec, J1K-2R1

Abstract

In this tutorial we will tackle the problem of electronic correlations in quasi-one-dimensional organic superconductors. We will go through different pieces of experimental evidence showing the range of applicability of the Fermi and Luttinger liquid descriptions of the normal phase of the Bechgaard salts series and their sulfur analogs.

Keywords : organic superconductors, many-body theories, magnetic measurements, magnetic phase transitions.

1. Introduction

In solid-state physics the traditional approach to understand ordinary metals relies on the Landau theory of Fermi liquid. The concept of quasi-particles put forth by Landau proved to be quite successful in describing low-energy excitations, which effectively behave like non-interacting electrons. Besides the possibility of long range order which limits its range of applicability, the Fermi liquid theory turns out to be highly sensitive to the spatial dimensionality of the electron system. This is especially true for purely one-dimensional systems where the Landau Fermi liquid theory breaks down. It is pretty well understood that in one dimension there are no single-particle states that adiabatically connect with the non-interacting electrons. Instead elementary excitations are made of collective modes of bosonic character [1].

The possibility that such non-Fermi liquid correlation effects may be relevant to the description of the normal phase of real materials like quasi-one-dimensional organic conductors has attracted lot of interest over the past two decades [2]. However, since these systems are not strictly one-dimensional, this raises the delicate question of the extent to which Fermi and non-Fermi liquid concepts are relevant to the understanding of the normal phase of these molecular compounds. In this tutorial we will pursue this issue for the well known isostructural series of sulfur-based (TMTTF)₂X and selenium-based (Bechgaard salts) (TMTSF)₂X organic conductors. We will review recent progress made in the analysis of the NMR spin-lattice relaxation rate, magnetic susceptibility and transport measurements in connection with correlation effects and non-Fermi liquid features found in these strongly anisotropic materials.

2. The low-field phase diagram

Following the synthesis of the isostructural sulfur (TMTTF)₂X and selenide (TMTSF)₂X series of quasi-1D organic conductors, it was soon recognized that a remarkable continuity can be drawn whenever their phase diagrams are combined as a function of applied hydrostatic pressure or anion (X= PF₆, AsF₆, Br...) substitution. Depending on the choice of the anion at ambient pressure, members of the sulfur series can develop either spin-Peierls or commensurate/localized antiferromagnetic long range order whereas either itinerant antiferromagnetism (SDW) or superconductivity can be found for the selenide series under similar pressure conditions. Under pressure, however, the spin-Peierls and localized antiferromagnetic orderings alternately become unstable to the benefit of phases found in selenides thereby ensuring the characteristic sequence SP → AF → S of transitions shown in Figure 1.

The survey of existing results at low magnetic fields reveals that the critical temperature bracket for AF ordering is $T_N \approx 1 \dots 24\text{K}$ (the highest T_N being found in sulfur series) and $T_{SP} \approx 8 \dots 19\text{K}$ for the spin-Peierls ordering, while for supeconductivity, it is scarcely more than 1K.

The study of the normal phase has shed some special light on the central role played by antiferromagnetism in the phase diagram of these quasi-1D materials. This is particularly revealing for (TMTTF)₂X compounds for which precursors to magnetic ordering become manifest at a characteristic temperature T_p that can be in magnitude far above T_N under low pressure conditions. The scale T_p signals the loss of metallic character and in most cases the thermal activation of carriers corresponding to a gap $\Delta_p \approx 2 \dots 3T_p$ in the normal phase temperature dependent electrical resistivity (Figure 2).

This contrasts with the temperature variation of magnetic susceptibility shown in Figure 3, which indicates that long wavelength spin degrees of freedom remain unaffected

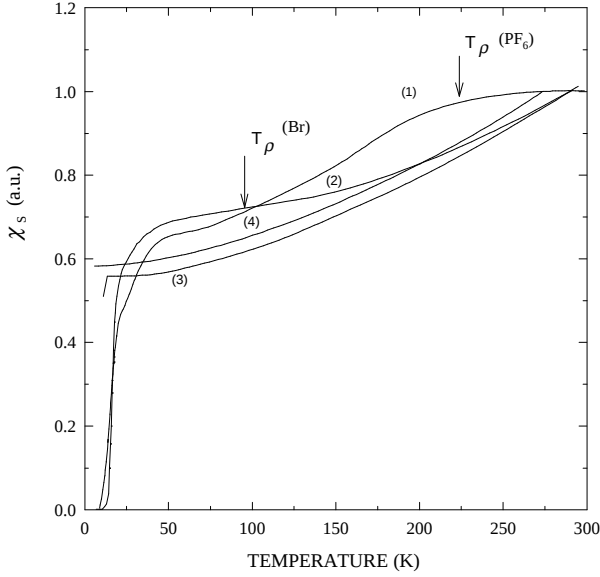


Figure 3: Temperature dependence of the magnetic susceptibility of (TMTTF)₂PF₆ (1), (TMTTF)₂Br (2), (TMTSF)₂PF₆ (3) and (TMTSF)₂ClO₄ (4) at ambient pressure.

Luttinger liquid prediction for T_1^{-1} takes the form:

$$T_1^{-1} = C_0 T \chi_s^2(T) + C_1 T^{1-\gamma}, \quad (2)$$

which consists of contributions coming from uniform ($q = 0$) and antiferromagnetic ($q \approx 2k_F$) spin fluctuations. Both generate deviations with respect to the Korringa law $(T_1 T)^{-1} = \text{constant}$, found in ordinary metals with weak interactions. The uniform contribution, albeit related to the non-singular temperature dependent magnetic spin susceptibility, dominates at high temperature while the antiferromagnetic power law enhancement $(T_1 T)^{-1} \sim C_1 T^{-\gamma}$ in principle allows to extract the Luttinger liquid exponent γ . The combination of $\chi_s(T)$ and T_1^{-1} measurements then proves to be a powerful tool in the analysis of correlation effects in the normal state of low-dimensional organic conductors [9, 10, 11].

This ability has been remarkably illustrated in the case of (TMTTF)₂X compounds as typified by the selected results shown in Figure 5. Let us consider for example the normal state of the spin-Peierls system (TMTTF)₂PF₆ at ambient pressure. This compound presents a well defined resistivity minimum at $T_\rho \approx 220\text{K}$ [12], whereas the spin susceptibility $\chi_s(T)$ shown in Figure 3, produces a regular downward slope as the temperature is lowered. As for the T_1^{-1} temperature profile given in Figure 5, it also presents a monotonic decrease with an upward curvature down to the low temperature region where T_1^{-1} shows signs of saturation. This persists down to 40K or so, below which the system is dominated by strong spin-Peierls lattice correlations, as borne out by x-ray experiments [13]. Plotting T_1^{-1} vs $T \chi_s^2(T)$ in the temperature domain above 40K (where lattice fluctuations are weak), one finds that the Luttinger liquid prediction (2) with $\gamma = 1$ ($K_\rho = 0$) is rigorously obeyed (inset of Figure 5). Therefore the existence of a constant term in T_1^{-1} over all the temperature

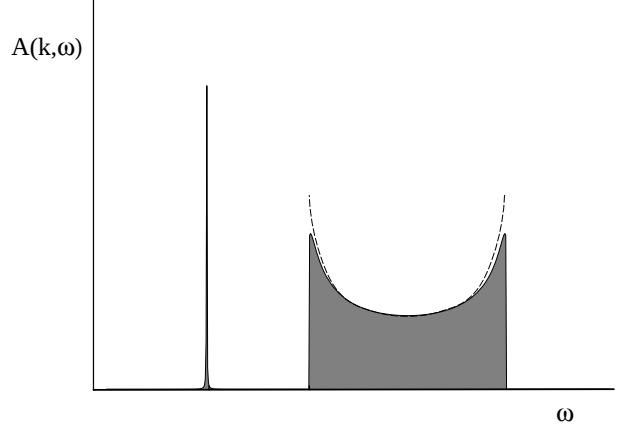


Figure 4: Schematic one-particle spectral weight of a Luttinger liquid for the one-dimensional case (dashed line). In the quasi-one-dimensional case, the single-particle dimensionality crossover introduces a quasi-particle peak and the smearing of the power-law singularities.

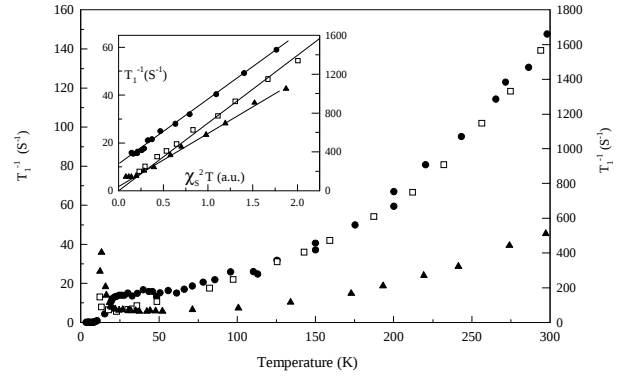


Figure 5: T_1^{-1} vs T for (TMTTF)₂PF₆ (circles, ¹³C, left scale), (TMTTF)₂Br (triangles, ¹³C, left scale) and (TMTSF)₂PF₆ (open squares, ⁷⁷Se, right scale) at $P = 1\text{bar}$. In the inset T_1^{-1} vs $T \chi_s^2$ in the normal phase using the data of Figure 3. After Refs. [10,11].

domain considered soundly supports the existence of a Mott-Hubbard localization which essentially coincides to a Luttinger liquid with a charge gap and gapless spin excitations. Similar features have been tracked down in other members of the same series. In this connection we have reproduced in Figure 5, the T_1^{-1} temperature profile obtained for (TMTTF)₂Br where $T_\rho \sim 100\text{K}$ and $T_N \approx 15\text{K}$ [11]. Using the susceptibility data of Figure 3, the corresponding T_1^{-1} vs $T \chi_s^2(T)$ plot in the inset shows that in the normal phase (above the critical domain taking place below 30K), the expression (2) with $\gamma = 1$ is again fully obeyed but with C_1 being smaller [11].

2.3. Interchain coupling and the one- and two-particle instability of the Luttinger liquid

Given the quasi-1D character of materials like (TMTTF)₂X, the presence of long range ordering invariably indicates that the Luttinger liquid becomes unstable at low temperature.

It can be shown, however, that it can still influence the formation of critical ordering in this case antiferromagnetic. The microscopic source of instability of the Luttinger liquid comes from the interchain coupling and in particular the interchain single particle hopping $t_{\perp}$ [14, 15, 16]. This coupling is essential to the propagation of antiferromagnetic correlations perpendicular to the chains. According to band calculations [17], however, $t_{\perp} \lesssim 100\text{K}$ in sulfur compounds, which means that a coherent interchain single particle hopping (band motion) is made irrelevant owing to the presence of a large charge gap $\Delta_{\rho} > t_{\perp}$ in the normal phase [18]. Nevertheless, bound electron-hole pairs can tunnel to neighboring chains via the virtual hops of single carriers leading to a perpendicular antiferromagnetic kinetic exchange coupling $J_{\perp} \approx 2\pi v_F t_{\perp}^{*2}/\Delta_{\rho}^2$ (where $t_{\perp}^*$ stands as a renormalized value of $t_{\perp}$). The critical ordering temperature T_N is obtained by considering the effect of $J_{\perp}$ in molecular field approximation whereas intrachain correlations are treated exactly. One then gets the Stoner criteria $1 - J_{\perp}\chi(2k_F, T_N) = 0$ for T_N . Now using the exact power law expression $\chi(2k_F, T) \sim T^{-1}$ at $T \ll T_{\rho}$, one readily finds

$$T_N \approx t_{\perp}^{*2}/\Delta_{\rho}, \quad (3)$$

which *increases* as Δ_{ρ} or T_{ρ} *decreases* under pressure. T_{ρ} will merge in the critical domain of the transition and becomes irrelevant. In this range of intermediate pressure, the normal phase is metallic corresponding to a Luttinger liquid with gapless spin and charge excitations (Figure 1). As for the interchain exchange interaction, it takes the form $J_{\perp} \approx 2\pi v_F \tilde{g}^{*2} t_{\perp}^{*2}/T^2$, where $\tilde{g}$ is a normalized effective electron-electron coupling constant divided by πv_F . Therefore whenever $T > T_{x1} \approx t_{\perp}^*/2$ (that is above the single-particle dimensionality crossover temperature that marks the thermal deconfinement of along the stacks), $J_{\perp}$ turns out to be still active in the development of long range order. The Stoner criteria in this case leads to

$$T_N \approx 2\tilde{g}^* T_{x1}, \quad (4)$$

which *decreases* through $\tilde{g}^*$ under pressure [15, 16]. Ultimately, the T_N pressure profile will show a maximum at a critical pressure P_m where T_{ρ} merges into the critical domain. A maximum of this kind has been found in all sulfur compounds that were the subject of pressure studies. The results of Klemme *et al.* [19] for the (TMTTF)₂Br, which are reproduced in Figure 6, indeed illustrate how the interchain exchange coupled to the Luttinger liquids of isolated chains give a controlled description of the antiferromagnetic transition in sulfur compounds up to intermediate pressure.

The interchain kinetic exchange will keep its key role for long range ordering as long as the carriers stay thermally confined in the transverse direction. In fact, as one moves away from the maximum of T_N by increasing pressure, the downward renormalization of $t_{\perp}^*$ gets weaker due to a reduction of intrachain many-body effects. This progressively raises the single-particle dimensionality crossover temperature T_{x1} up to a point where the exchange-induced temperature scale for critical fluctuations $T_{f1} \approx 2T_N$, as obtained from (4), becomes smaller than T_{x1} [20]. This range of pressure then shows electronic deconfinement which is a one-particle type of instability of the Luttinger liquid that announces the formation of a *Fermi liquid* component

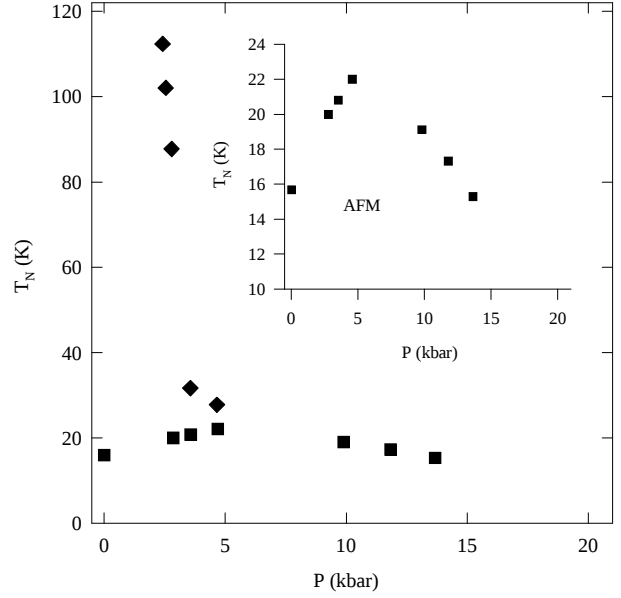


Figure 6: T_N as a function of pressure for (TMTTF)₂Br. In the inset the pressure profile of T_N near P_m . After Klemme *et al.*, Ref.[19].

[15, 16, 21]. It follows that the two-dimensional character of nesting properties at the wavevector $\mathbf{Q}_0 = (2k_F, a\pi)$ picks up some coherence below T_{x1} which can no longer be neglected in the evaluation of the critical temperature T_N . Here the modulation wavevector $\mathbf{Q}_0$ is found to be incommensurate for the sulfur compounds at high pressure and in the selenides as well where ($a \approx .24$) [19, 22]. From the point of view of perturbation theory, such a coherence marks a progressive decoupling of infrared singularities pertaining to the “ $2k_F$ ” density-wave and superconducting Cooper channels whose interference is at the heart of the existence of a Luttinger liquid in one dimension. Thus for those degrees of freedom involved in the Fermi liquid component below T_{x1} , the elementary logarithmic infrared singularity of the spin-density-wave channel, which reads $\chi^0(\mathbf{Q}_0, T) \approx (2\pi v_F)^{-1} \ln(T_{x1}/T)$ for perfect nesting conditions, may be singled out and summed up at the one-loop ladder level of the perturbation theory. This yields the Stoner criteria $1 - \lambda^* \chi^0(\mathbf{Q}_0, T_N) = 0$, from which one obtains

$$T_N \approx T_{x1} e^{-2/\tilde{\lambda}^*}, \quad (5)$$

where $\tilde{\lambda}^*$ stands as an effective coupling constant that combines the renormalized intrachain interactions *and* the interchain exchange at the energy scale T_{x1} [15, 16]. Nesting properties below T_{x1} , however, rely on the electron-hole symmetry relation $\epsilon(\mathbf{k}) = -\epsilon(\mathbf{k} + \mathbf{Q}_0)$ at $\mathbf{Q}_0$, which turns out to be vulnerable to small perturbations that are present in the actual spectrum $\epsilon(\mathbf{k})$. Next-nearest-neighbor interchain hopping $t_{\perp,2}$ is often used to parametrize such an effect that cuts off the logarithmic singularity in $\chi^0(\mathbf{Q}_0, T)$, thereby reducing T_N . A perturbation like $t_{\perp,2}$ is quite sensitive to pressure and only few kilobars are needed to bring T_N down to zero.

It is now generally admitted that this simple mechanism is responsible for the frustration of the incommensurate

spin-density-wave phase found in selenides (sulfur) series at low (high) pressure [24, 23]. It should be stressed, however, that the presence of nesting frustration indicates that a Fermi liquid component is present in the normal phase thus confirming that the characteristic scale T_{x1} for deconfinement really emerges in a pressure range that can safely be located somewhere between P_m and P_c (Figure 1). Since transients are likely to be associated with such a crossover, the deconfinement is not sharply defined so that at a given pressure it should be considered as somewhat spreaded in temperature. For systems like $(\text{TMTSF})_2\text{X}$ at ambient pressure or $(\text{TMTTF})_2\text{X}$ at relatively high pressure, the accepted range of values for T_{x1} may differ a lot from author to author. Following the example of what has been done for sulfur compounds at low pressure it is thus preferable to look at experiments in order to detect deviations to the Fermi liquid picture in the normal phase. If one looks for example at the existing results for the temperature dependent T_1^{-1} and χ_s in the ambient pressure metallic phase of $(\text{TMTSF})_2\text{PF}_6$ ($T_N \approx 12\text{K}$), one observes from Figure 5 that deviations with respect to the $T\chi_s^2$ law become perceptible below $T\chi_s^2 \approx 1$, which corresponds to the actual temperature scale $T < 200\text{K}$. According to (2), one can then extract the antiferromagnetic part of the enhancement in $(T_1T)^{-1}$ which is found to have increased by a factor 5 at $T \approx 50\text{K}$, namely well outside the critical domain of the transition. This non-critical enhancement is thus too large to result from Fermi liquid conditions in which case $(T_1T)^{-1}[\mathbf{Q}_0] \sim \text{constant}$ and should follow a Korringa law. This brings us to infer that a Luttinger liquid picture of the normal phase would still persist at 50K in $(\text{TMTSF})_2\text{PF}_6$ at ambient pressure suggesting an upper bound value $T_{x1} < 50\text{K}$ for deconfinement. It is worth noting here that a similar enhancement has been detected in $(\text{TMTTF})_2\text{Br}$ at 13 kbar [11].

A connection has been made between these correlation effects and the anomalous photoemission data of Dardel *et al.* [8], which reveal a strong depression of the quasi-particle weight at the Fermi level for $(\text{TMTSF})_2\text{PF}_6$ at 50K . Deviations from the Drude response in optical conductivity of the normal phase of these materials have also been related to the presence of antiferromagnetic correlations, though their influence on transport properties is in general poorly understood [25].

3. Confinement under magnetic field

When a transverse magnetic field is applied in the pressure domain $P \gtrsim P_c$ for compounds like $(\text{TMTSF})_2\text{PF}_6$ and $\text{TMTSF}_2\text{ClO}_4$, another sector of the phase diagram opens up for which the concept of the Luttinger liquid may be relevant to the description of the normal phase. When the magnetic field is increased along the c^* direction, this prompts an anomalously large longitudinal resistance and a upturn in resistivity at a temperature $T_\rho(H)$. As shown in Figure 7 for the $(\text{TMTTF})_2\text{PF}_6$ under 8.5 kbar and field up to 12T [27], the resistivity minimum moves away from the critical line of the cascade of field-induced-spin-density-wave phases. This giant magnetoresistance was soon recognized as one of the anomalous feature of the normal phase of these materials under field that does not entirely conform

to classical magnetotransport [26].

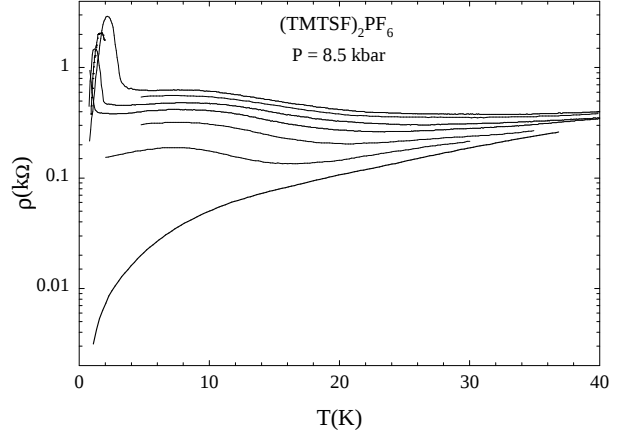


Figure 7: Longitudinal resistance of $(\text{TMTSF})_2\text{PF}_6$ at $P = 8.5\text{ kbar}$ as a function of temperature and magnetic field $H = 0, 2, 3, 6, 8, 11, 12.5\text{T}$. After Ref. [27].

It was recently proposed that the unidimensionalization of electron motion under field not only bypasses the effect of $t_{\perp,2}$ (in inducing perfect but quantized nesting conditions that are responsible for the cascade of FSDW phases [28]), but improves longitudinal nesting conditions at $(2k_F, 0)$ as well. This gradually reactivates the singular flow of one-dimensional many-body effects below T_{x1} [29]. Since the dimerization of the organic stacks, though weak, makes longitudinal electron-electron unklapp scattering relevant (the g_3 coupling in the “g-ology” notation), it may lead to a singular growth of the electron-electron scattering rate which takes the form $\tau_e^{-1} \sim T[g_3(T)]^2$. This may cause an upturn in resistivity which clearly is reminiscent of the one found in sulfur series at low pressure (Figure 2) [31]. At variance with the more one-dimensional sulfur compounds, however, the restoration of longitudinal nesting is only gradual under a magnetic field, precluding the formation of a sharp charge gap that would entirely destroy the Fermi liquid component of the normal phase. The restoration of the Luttinger liquid under a field, though gradual, should have important consequences on spin correlations, especially those at $2k_F$. Figure 8 shows ^{77}Se T_1^{-1} vs T and the Knight shift K_s ($TK_s^2 \propto T\chi_s^2$) data of $\text{TMTSF}_2\text{ClO}_4$ at ambient pressure and for two different fields ($H = 6\text{T}$, with $T_\rho \approx 5\text{K}$ and $H = 15\text{T}$, with $T_\rho \approx 15\text{K}$) [29, 30].

As one can see from the Figure 8, T_1^{-1} is dominated by the uniform TK_s^2 component at sufficiently high temperature but deviations connected to the antiferromagnetic part of the relaxation emerge at low temperature. This enhancement appears to be quite distinct from the critical T_1^{-1} growth near the FSDW transitions taking place at $T_N \approx 2.8\text{K}$ (6T) and 4.4K (15T). Following the analysis made in Ref. [29], the relaxation rate in the normal phase can be very well described by an expression of the form

$$T_1^{-1} \approx C_0 T \chi_s^2(T) + C_1(H), \quad (6)$$

where $C_1(H)$ is a temperature independent contribution that increases as $T_\rho(H)$ under a magnetic field. This is quite similar to what is found in the sulfur compounds at higher

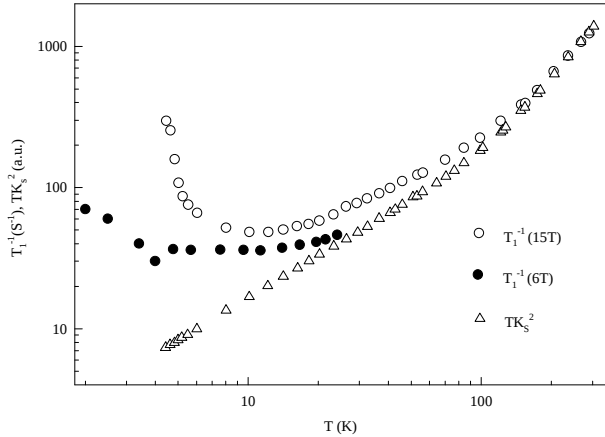


Figure 8: Temperature dependence of ^{77}Se nuclear relaxation rate and Knight shift for $(\text{TMTSF})_2\text{ClO}_4$ under magnetic field along c^* at ambient pressure. After Refs. [29,30].

temperature (see Figure 5). These results suggest that the progressive unidimensionalization of low-energy states under a field may gradually reactivate Luttinger liquid features in the normal phase precursor to the cascade of FSDW.

Ultimately, this emphasizes once again that the selenium series and their sulfur analogs are closely related to one another.

Acknowledgments I would like to thank my colleagues in Orsay, Grenoble and Sherbrooke for their close collaboration on various aspects of this work.

References

- [1] S. Tomanaga, Prog. Theor. Phys. **5**, 544 (1950); J. Luttinger, J. Math. Phys. **4**, 1154 (1963); D. C. Mattis and E. H. Lieb, J. Math. Phys. **6**, 304 (1965).
- [2] See for example, *Organic Conductors, Fundamentals and Applications*, J. P. Farges ed. (Dekker, New York, 1994); *Proceedings of the NATO Advanced Study Institute on "Low Dimensional Conductors and Superconductors"*, Vol. **155**, edited by D. Jérôme and L. G. Caron (Plenum Publishing Corporation, New York, N.Y., 1987).
- [3] F. D. M. Haldane, J. Phys. C: Solid State Phys. **14**, 2585 (1981).
- [4] D. C. Mattis, Proceedings of ICSM'96; *The Many-Body Problem, (An Encyclopedia of Exactly Solved Models in One Dimension)*, D.C. Mattis, ed. (World Scientific, 1993).
- [5] See for example, J. Voit, Rep. Prog. Phys. **58**, 977 (1995); V. J. Emery, in *Highly Conducting One-Dimensional Solids*, edited by J. T. Devreese and R. P. Evrard, and V. E. van Doren (Plenum, New York, 1979); J. Solyom, Adv. Phys. **28**, 201(1979).
- [6] V.J. Emery *et al.*, Phys. Rev. Lett. **48**, 1039 (1982).
- [7] F. Castet *et al.*, J. Physique I France, **6**, 583 (1996).
- [8] B. Dardel *et al.*, Europhys. Lett. **24**, 687 (1993).
- [9] C. Bourbonnais *et al.*, Phys. Rev. Lett. **62**, 1532 (1989).
- [10] C. Bourbonnais, J. Physique (France) I, **3**, 143 (1993).
- [11] P. Wzietek *et al.*, J. Physique I (France) **3**, 171 (1993).
- [12] C. Coulon *et al.*, J. Physique (France) **42**, 1059 (1982).
- [13] J. P. Pouget *et al.*, Mol. Cryst. Liq. Cryst. **79**, 129 (1982) and Proc. of ICSM'96.

- [14] Y. Firsov *et al.*, Phys. Rep. **126** 245 (1985).
- [15] C. Bourbonnais and L.G. Caron, Int. Journ. Mod. Phys. B **5** 1033 (1991); D. Boies *et al.*, Phys. Rev. Lett. **74**, 968 (1995).
- [16] C. Bourbonnais, Proc. of "Ecole de Physique Théorique, Les Houches", Session LVI (1991), *Strongly interacting Fermions and High T_c Superconductivity Superconductors*, B. Doucot and J. Zinn-Justin, eds. Elseviers Science (1995), P. 307.
- [17] P. M. Grant, J. Physique Coll. **44**, C3-847 (1983); L. Ducasse *et al.*, J. Phys. C: Solid State Phys. **18**, L-947 (1985).
- [18] S. Brazovskii and V. Yakovenko, Sov. Phys. JETP **62**, 1340 (1985).
- [19] B. J. Klemme *et al.*, Phys. Rev. Lett. **75**, 2408 (1995); See also, S. Brown Proc. of ICSM'96.
- [20] T_{fl} actually stands as a two-particle crossover temperature for the Luttinger liquid which is noted as T_{x2} in Ref.[15, 16].
- [21] Here we adopt a description of dimensionality crossovers that neglects transients which can be important for fermions.
- [22] T. Takahashi *et al.*, Physica **143B**, 417 (1986); J. M. Delrieu *et al.*, *Ibid.*, 412; E.Barthel *et al.*, Phys. Rev. Lett. **71**, 2825 (1993).
- [23] Chr. Seidel and V. N. Prigodin, J. Physique Lett. **44**, L403 (1983).
- [24] T. Ishiguro and K. Yamaji, *Organic Superconductors*, Springer-Verlag Series in Solid-State Science, Vol. **88** (Springer-Verlag, Berlin Heidelberg, 1990).
- [25] M. Dressel *et al.*, Phys. Rev. Lett. **77**, 398 (1996); Cao and T. Timusk, preprint (1996).
- [26] D. Jerome and H. J. Schulz, Adv. Phys. **31**, 299 (1982).
- [27] L. Balicas *et al.*, Orsay unpublished work.
- [28] L. P. Gorkov and A. G. Lebed, J. Phys. (Paris) Lett. **45** L433 (1984); M. Hritier *et al.*, J. Phys. (Paris) Lett. **45**, L943 (1984).
- [29] K. Behnia *et al.*, Phys. Rev. Lett. **74**, 5272 (1995).
- [30] C. Berthier *et al.*, unpublished results.
- [31] A different interpretation based on quasi-one-dimensional nesting of the Fermi surface has been proposed by L. P. Gorkov, Europhys. Lett., **31**, 49 (1995).